


# Speeds and Feeds for Drill Mills

## Fractional

### \* Chamfering \*

Type	Rc Hardness	SFM (Vc)		CHIPLOAD PER FLUTE (Fz)				
		154M, 154MA 152M, 152MA	1600 152D, 152DA	3/32" - 1/8"	1/8" - 1/4"	1/4" - 3/8"	3/8" - 1/2"	1/2" - 3/4"
<b>COBALT BASE ALLOYS</b>								
Powdered Metal, Stellite, Hs-21, Haynes 25/188, X-40, L-605	< 35	175 - 225	150 - 200	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"	.0020" - .0040"
	> 35	125 - 175	100 - 150	.0002" - .0004"	.0003" - .0005"	.0005" - .0015"	.0010" - .0020"	.0010" - .0030"
<b>NICKEL BASE ALLOYS</b>								
Invar, Kovar, Inconel-625/718, Waspalloy, Rene, Hastalloy, A286	< 35	125 - 175	100 - 150	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"	.0020" - .0040"
	> 35	70 - 115	70 - 100	.0002" - .0004"	.0003" - .0005"	.0005" - .0015"	.0010" - .0020"	.0010" - .0030"
<b>TITANIUM ALLOYS</b>								
Commercially Pure, 6Al-4V, Astm 1/2/3, 6Al-25N-4Zr-2Mo-Si	< 35	200 - 300	125 - 250	.0005" - .0010"	.0007" - .0015"	.0010" - .0025"	.0015" - .0040"	.0030" - .0050"
	> 35	175 - 225	150 - 200	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"	.0020" - .0040"
<b>STAINLESS STEELS</b>								
13/8, 15/5, 17-4, pH Types	< 35	150 - 250	100 - 150	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"	.0020" - .0040"
	> 35	125 - 175	80 - 150	.0002" - .0004"	.0003" - .0005"	.0005" - .0015"	.0010" - .0020"	.0010" - .0030"
Inox, 200 Series, 300 Series	< 35	200 - 250	125 - 175	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"	.0020" - .0040"
	> 35	150 - 200	100 - 150	.0002" - .0004"	.0003" - .0005"	.0005" - .0015"	.0010" - .0020"	.0010" - .0030"
304L, 316L, Nitronic 50, Inox	< 35	90 - 125	80 - 120	.0003" - .0006"	.0005" - .0008"	.0008" - .0015"	.0010" - .0020"	.0020" - .0040"
	> 35	75 - 110	60 - 90	.0002" - .0004"	.0003" - .0005"	.0005" - .0010"	.0010" - .0015"	.0010" - .0030"
400 Series	< 35	150 - 250	100 - 150	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"	.0020" - .0040"
	> 35	125 - 175	80 - 150	.0002" - .0004"	.0003" - .0005"	.0005" - .0015"	.0010" - .0020"	.0010" - .0030"
<b>HIGH STRENGTH TOOL STEELS</b>								
4140, 4340, 6150, 5210, A2, D2, P20, H11, H13, S2, O1	< 30	150 - 225	125 - 175	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"	.0020" - .0040"
	30 - 38	90 - 125	80 - 120	.0002" - .0004"	.0003" - .0005"	.0005" - .0015"	.0010" - .0020"	.0010" - .0030"
	> 38	60 - 90	40 - 70	.0002" - .0003"	.0002" - .0004"	.0003" - .0006"	.0005" - .0010"	.0006" - .0020"
<b>TOOL STEELS</b>								
200, 250, 300, 8620, A36, 12L14, 1018, 1020	< 35	175 - 250	150 - 200	.0005" - .0010"	.0007" - .0015"	.0010" - .0025"	.0015" - .0040"	.0030" - .0050"
	> 35	100 - 175	100 - 150	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"	.0020" - .0040"
<b>CAST MATERIAL</b>								
Steel, Iron		250 - 350	175 - 250	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Aluminum		250 - 350	250 - 350	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
<b>ALUMINUM</b>								
Aircraft Grade (6061, 7075)		350 - 500	300 - 400	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
<b>COPPER</b>								
Copper Alloys		250 - 350	150 - 300	.0005" - .0010"	.0007" - .0015"	.0010" - .0025"	.0015" - .0035"	.0020" - .0050"
<b>BRASS, BRONZE</b>								
Brass, Aluminum/Bronze, Low Silicon Bronze		250 - 350	150 - 300	.0005" - .0010"	.0007" - .0015"	.0010" - .0025"	.0015" - .0035"	.0020" - .0050"
<b>COMPOSITE MATERIAL</b>								
Glass Epoxy, Fiberglass, Plastics		250 - 450	200 - 400	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Graphite, G10, Carbon Fiber		300 - 500	250 - 450	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"

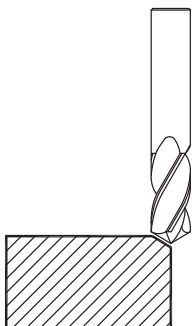

*Chamfering a corner*

**DRILL MILL USES:**

**Chamfering** - for all metals, use general milling speeds and feeds. Depending on depth, use diameter at top of part to determine chipload. For example, if using 1/4" diameter, 90° point and depth is 1/8", calculate the chipload based on 1/8" diameter.


**NOTE - ABOVE ARE STARTING PARAMETERS ONLY. HIGHER RESULTS MAY BE ACHIEVED WITH OPTIMUM CONDITIONS.**

# Speeds and Feeds for Drill Mills

## Fractional

### \* Through Hole \*

Type	Rc Hardness	SFM (Vc)		CHIPLOAD PER FLUTE (Fz)			
		152M, 152MA 154M, 154MA	152D, 152DA	1/8" - 1/4"	1/4" - 3/8"	3/8" - 1/2"	1/2" - 3/4"
<b>TITANIUM ALLOYS</b>							
Commercially Pure, 6Al-4V, Astm 1/2/3, 6Al-25N-4Zr-2Mo-Si		-	125 - 250	.0007" - .0015"	.0010" - .0025"	.0015" - .0040"	.0030" - .0050"
<b>STAINLESS STEELS</b>							
13/8, 15/5, 17-4, pH Types	< 35 > 35	- -	100 - 150 80 - 150	.0005" - .0010" .0003" - .0005"	.0008" - .0020" .0005" - .0015"	.0010" - .0030" .0010" - .0020"	.0020" - .0040" .0010" - .0030"
<b>HIGH STRENGTH TOOL STEELS</b>							
4140, 4340, 6150, 5210, A2, D2, P20, H11, H13, S2, O1	< 30 30 - 38	-	125 - 175 80 - 120	.0005" - .0010" .0003" - .0005"	.0008" - .0020" .0005" - .0015"	.0010" - .0030" .0010" - .0020"	.0020" - .0040" .0010" - .0030"
<b>MEDIUM ALLOY TOOL STEELS</b>							
200, 250, 300, 8620	< 35 > 35	- -	150 - 200 100 - 150	.0007" - .0015" .0005" - .0010"	.0010" - .0025" .0008" - .0020"	.0015" - .0040" .0010" - .0030"	.0030" - .0050" .0020" - .0040"
<b>CARBON STEELS</b>							
A36, 12L14, 1000's, 1100's, 1300's	< 35 > 35	175 - 250 -	150 - 200 100 - 150	.0007" - .0015" .0005" - .0010"	.0010" - .0025" .0008" - .0020"	.0015" - .0040" .0010" - .0030"	.0030" - .0050" .0020" - .0040"
<b>CAST MATERIAL</b>							
Steel		-	175 - 250	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Ductile Iron		-	175 - 250	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Gray Iron		-	175 - 250	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Aluminum		250 - 350	250 - 350	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
<b>ALUMINUM</b>							
Aircraft Grade (6061, 7075)		350 - 500	300 - 400	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
<b>MAGNESIUM</b>							
		250 - 400	250 - 350	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
<b>COPPER</b>							
Copper Alloys		250 - 350	150 - 300	.0007" - .0015"	.0010" - .0025"	.0015" - .0035"	.0020" - .0050"
<b>BRASS, BRONZE</b>							
Brass, Aluminum/Bronze, Low Silicon Bronze		250 - 350	150 - 300	.0007" - .0015"	.0010" - .0025"	.0015" - .0035"	.0020" - .0050"
<b>COMPOSITE MATERIAL</b>							
Glass Epoxy, Fiberglass, Plastics		250 - 450	200 - 400	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Graphite, G10, Carbon Fiber		300 - 500	250 - 450	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"

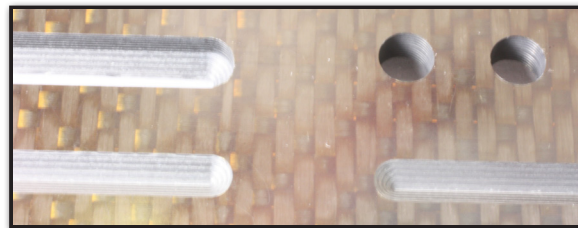


**NOTE - ABOVE ARE STARTING PARAMETERS ONLY. HIGHER RESULTS MAY BE ACHIEVED WITH OPTIMUM CONDITIONS.**

# Speeds and Feeds for Drill Mills

## Fractional

### \* Solids \*

Type	Rc Hardness	SFM (Vc)	CHIPLOAD PER FLUTE (Fz)			
		152M, 152MA 154M, 154MA	1/8" - 1/4"	1/4" - 3/8"	3/8" - 1/2"	1/2" - 3/4"
<b>STAINLESS STEELS</b>						
13/8, 15/5, 17-4, pH Types	< 35	125 - 175	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"
400 Series	< 35	125 - 175	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"
<b>HIGH STRENGTH TOOL STEELS</b>						
4140, 4340, 6150, 5210, A2, D2, P20, H11, H13, S2, O1	< 30	125 - 200	.0003" - .0008"	.0005" - .0010"	.0008" - .0020"	.0010" - .0030"
	30 - 38	90 - 125	.0002" - .0004"	.0003" - .0005"	.0005" - .0015"	.0010" - .0020"
<b>MEDIUM ALLOY TOOL STEELS</b>						
200, 250, 300	< 35	150 - 225	.0005" - .0010"	.0007" - .0015"	.0010" - .0025"	.0015" - .0040"
<b>CARBON STEELS</b>						
A36, 1000's, 1100's, 1300's	< 35	150 - 250	.0005" - .0010"	.0007" - .0015"	.0010" - .0025"	.0015" - .0040"
<b>CAST MATERIAL</b>						
Steel		150 - 250	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"
Aluminum		200 - 350	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"
<b>ALUMINUM</b>						
Aircraft Grade (6061, 7075)		250 - 400	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"
<b>MAGNESIUM</b>						
		250 - 400	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"
<b>COPPER</b>						
Copper Alloys		250 - 350	.0005" - .0010"	.0007" - .0015"	.0010" - .0025"	.0015" - .0035"
<b>BRASS, BRONZE</b>						
Brass, Aluminum/Bronze, Low Silicon Bronze		250 - 350	.0005" - .0010"	.0007" - .0015"	.0010" - .0025"	.0015" - .0035"
<b>COMPOSITE MATERIAL</b>						
Glass Epoxy, Fiberglass, Plastics		250 - 450	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"
Graphite, G10, Carbon Fiber		300 - 500	.0007" - .0015"	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"

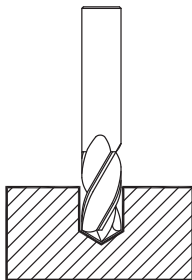

**DRILL MILL USES:**

*Solids* - primarily for use in composites and plastics.

**Slotting**

**NOTE - ABOVE ARE STARTING PARAMETERS ONLY. HIGHER RESULTS MAY BE ACHIEVED WITH OPTIMUM CONDITIONS.**